

## Rapid construction of an effective antifouling layer on a Au surface *via* electrodeposition†

Cite this: *Chem. Commun.*, 2014, 50, 6793

Bor-Ran Li,‡<sup>a</sup> Mo-Yuan Shen,‡<sup>a</sup> Hsiao-hua Yu<sup>b</sup> and Yaw-Kuen Li\*<sup>a</sup>

Received 20th February 2014,  
Accepted 6th May 2014

DOI: 10.1039/c4cc01329h

www.rsc.org/chemcomm

**A new approach to immobilize zwitterionic molecules rapidly and highly efficiently on a gold surface applies aniline-based electro-deposition. The zwitterion-functionalized antifouling surface enables a decrease of the adsorption of non-specific proteins by 95% from fetal bovine serum (FBS, 10%).**

Biosensors have drawn much attention because of their potential to greatly improve biomedical research,<sup>1–4</sup> drug discovery,<sup>5,6</sup> environmental monitoring,<sup>7</sup> and diagnosis of many diseases.<sup>8–10</sup> In particular, a biosensor applied to the clinical diagnosis of epidemic diseases,<sup>11</sup> long-term nursing of chronic diseases,<sup>12</sup> and early diagnosis of cancers<sup>13</sup> could save many lives around the world. To improve various properties of biosensors with the latest technology is hence of continual interest to engineers and scientists. The quartz crystal microbalance (QCM),<sup>14</sup> an ultra-sensitive balance capable of measuring changes in mass at the molecular level, is one of the most attractive biosensors that has been commercialized. The structure of a QCM chip is robust; the measurement is processed in real time, free of labels, and almost independent of the ionic strength. A QCM is thus supposed to be an ideal system for biological sensing, and has been established to detect various biomolecules *via* the specific recognition of target analytes with the corresponding receptors (*i.e.* antibodies) immobilized on the Au surface of the device.<sup>15</sup> The nonspecific binding between the proteins in a patient's serum and the Au surface of a QCM is a critical problem that might greatly decrease the sensitivity and reliability of the detection. To decrease the nonspecific interaction between the components of plasma and the Au surface is thus an important issue for sensitive and specific sensing of biological matrices.

Goda *et al.*<sup>16</sup> demonstrated that thiol-functionalized zwitterions were chemisorbed to form a self-assembled monolayer (SAM) on the Au surface of a QCM chip *via* a Au–S bond. *Via* ionic solvation, the zwitterionic layer can strongly trap water molecules on the surface of the chip. The expulsion of water molecules from between the protein and the zwitterion surface becomes difficult leading to the reduction of non-specific protein adsorption on the chip. The presence of the inert zwitterionic layer decreased the non-specific binding up to 60–70% from the dilute serum (10% fetal bovine serum, FBS), indicating that modifying a QCM surface with zwitterions is an ideal strategy to create antifouling platforms for sensitive and specific detection involving a clinical sample.<sup>17,18</sup> Although a thiol-SAM is readily prepared on the Au surface of a QCM chip on immersing the substrate in a dilute solution of zwitterionic thiols, the thiol-SAM process requires 12 to 72 h at room temperature.<sup>19,20</sup> A Au surface of high quality and pure reagents are essential to avoid defects in the monolayer formation.<sup>21</sup> Unlike the smooth Au surface on SPR, a bumpy sub-micrometre structure of a Au surface on a QCM chip is commonly observed because of its advantage of enlarging the binding area to enhance sensitivity.<sup>22</sup> Defects (*e.g.* monatomic vacancy islands) on the rough Au surface are easily formed upon modification of a zwitterionic layer using thiol-SAM approaches. Intermolecular electrostatic repulsion between zwitterionic molecules might also cause the formation of a non-uniform SAM layer that consequently produces a poor zwitterion density and results in a limited antifouling effect. The development of a new approach to decrease the duration of reaction and to achieve a uniform antifouling layer on the Au surface is hence highly desirable.

Here, we demonstrate a new approach to directly modify the zwitterionic molecule, dimethyl-ammonio propane-1-sulfonate (sulfobetaine or SB),<sup>23,24</sup> on the Au surface of the QCM chip *via* electrodeposition. In the first step, sulfobetaine (SB) is conjugated with an aniline functional group to form 3-[[4-aminophenyl]-dimethylammonio]propane-1-sulfonate (referred to as aminophenyl sulfobetaine or AP-SB in this report). Upon optimizing the conditions, AP-SB can be efficaciously synthesized in a yield >70%.


<sup>a</sup> Department of Applied Chemistry, National Chiao Tung University, Hsinchu, Taiwan. E-mail: ykl@cc.nctu.edu.tw

<sup>b</sup> Institute of Chemistry, Academia Sinica, Taipei, Taiwan

† Electronic supplementary information (ESI) available: Fig. S1–S6 and Section S1–S7. See DOI: 10.1039/c4cc01329h

‡ Bor-Ran Li and Mo-Yuan Shen made equal contributions to this work.



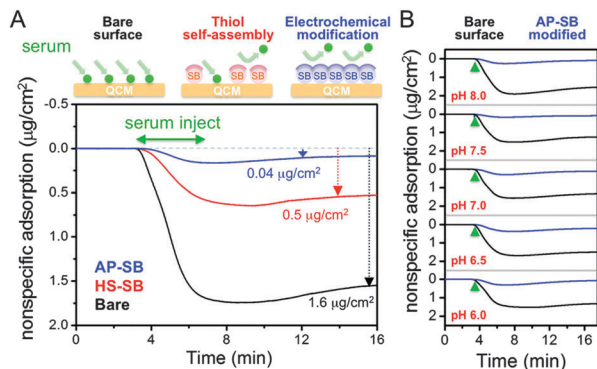


**Fig. 2** (A) Real-time recording of the  $\Delta$  frequency responses to FBS (10%) with AP-SB-electrodeposited (blue), HS-SB SAM-coated (red), and unmodified (black) QCM devices in PBS buffer (pH 7.2). (B) Comparison of responses of bare (black) and electrodeposited SB QCM devices to FBS (10%) at pH 6.0, 6.5, 7.0, 7.5 and 8.0. Green arrows indicate the point of FBS injection.

change/g,  $A$  = area of electrodes/cm<sup>2</sup>,  $\rho_q$  = density of quartz and  $\mu_q$  = shear modulus of quartz.

$$\Delta f = -\frac{2f_0^2}{A\sqrt{\rho_q\mu_q}}\Delta m \quad (3)$$

As the results in Fig. 2A show, QCM with the zwitterionic layer immobilized by electrodeposition is demonstrated to adsorb non-specific bound proteins ( $0.04 \mu\text{g cm}^{-2}$ ) (blue line) to a lesser extent than a bare ( $1.6 \mu\text{g cm}^{-2}$ ) (black line) surface or the one modified by the thiol-SAM approach ( $0.6 \mu\text{g cm}^{-2}$ ) (red line). As the  $pK_a$  of sulfonic acid is relatively low, the SB is expected to maintain a zwitterionic form in a wide range of pH. For this reason, a SB-modified QCM chip exhibits pH-independent antifouling ability, particularly in the pH range 6–8, the common conditions of bio-analysis or diagnosis (Fig. 2B). Since low ionic strength (<100 mM) may increase non-specific protein adsorption,<sup>28,29</sup> a high buffer concentration (150 mM) is employed in this study. The stability of the SB-modified chip is monitored for more than 2 weeks with no significant loss of the antifouling ability (Fig. S5, ESI†).

We utilized fluorescence images to display the antifouling ability of Au electrodes with and without the SB modification. We dropped a red fluorescent protein (mCherry) onto the silicon substrate with the micro-patterned Au electrodes. As the control experiment shows (Fig. 3A), a bare substrate without mCherry treatment revealed no fluorescence emission. After incubation for 1 h with the concentrated mCherry protein ( $10 \text{ mg mL}^{-1}$ , approximately equivalent to the concentration of total proteins in 10% serum), non-specific binding, resulting in red fluorescence, is clearly revealed on the bare Au electrodes (Fig. 3B), but almost no mCherry protein adhered to the electrode selectively coated with SB by electrodeposition (Fig. 3C). The relative fluorescence intensities in Fig. 3A(i), B(i), and C(i) quantified by the Photoshop program, is 0, 116, and 4, respectively. The bottom panels (Fig. 3A(ii), B(ii), and C(ii)) show bright-field images at the same positions. The red colour (not fluorescence)

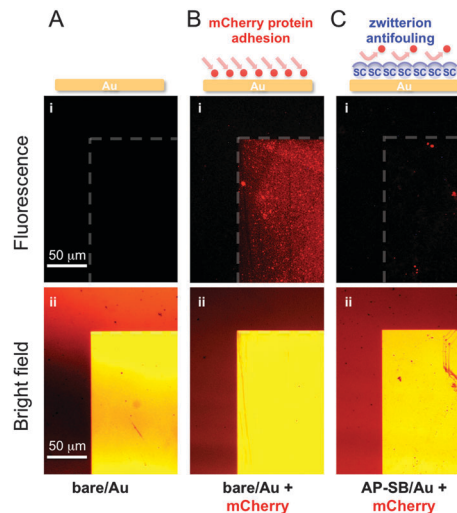

**Fig. 3** Images of adhesion of the mCherry fluorescent protein on a micro-patterned gold electrode on a photoresist-(LOR-5B)-preserved silicon substrate. (A) Fluorescent (i) and bright-field (ii) images of a bare Au electrode without mCherry treatment. (B) Images of a bare Au electrode incubated with the mCherry fluorescent protein ( $10 \text{ mg mL}^{-1}$ ) for 1 h. (C) Images of the AP-SB-modified Au electrode incubated with the mCherry fluorescent protein ( $10 \text{ mg mL}^{-1}$ ) for 1 h.

shown in these bright-field images resulted from the reflection of incident light.

In summary, we present a synthesis of an aniline-based zwitterionic molecule (AP-SB) in a high yield (>70%) that is demonstrated to be a key reagent to improve the surface modification of Au chips by electrodeposition. Relative to a conventional thiol-SAM approach, electrodeposition has the advantages of decreasing the duration of reaction from hours or even days to 3 min and increasing the SB modification density, resulting in significantly decreased non-specific binding up to  $95 \pm 3\%$  from the dilute FBS. The SB-modified chip clearly demonstrated much better antifouling properties than those of bare gold and the hydrophobic surface (Fig. S6, ESI†). The platform demonstrated herein is highly useful to improve the sensitivity and reliability of a biosensor using Au as the sensory chip. It is also useful for carbon,<sup>30</sup> ITO,<sup>31</sup> and other electrodes.<sup>32</sup>

The Ministry of Science and Technology of Taiwan (NSC 101-2120-M-009-011-CC1) and the Center for Interdisciplinary Science (CIS) of National Chiao Tung University of Taiwan under MOE 5Y50B project financially supported this research.

## Notes and references

- 1 J. Wang, *Chem. Rev.*, 2008, **108**, 814–825.
- 2 J. T. Sheu, C. C. Chen, K. S. Chang and Y. K. Li, *Biosens. Bioelectron.*, 2008, **23**, 1883–1886.
- 3 Y. Liu, X. Dong and P. Chen, *Chem. Rev.*, 2012, **41**, 2283–2307.
- 4 B. R. Li, C. C. Chen, R. U. Kumar and Y. T. Chen, *Analyst*, 2014, **139**, 1589–1608.
- 5 M. A. Cooper, *Nat. Rev. Drug Discovery*, 2002, **1**, 515–528.
- 6 M. F. Templin, D. Stoll, M. Schrenk, P. C. Traub, C. F. Vohringer and T. O. Joos, *Drug Discovery Today*, 2002, **7**, 815–822.
- 7 F. Long, A. Zhu and H. Shi, *Sensors*, 2013, **13**, 13928–13948.
- 8 K. I. Chen, B. R. Li and Y. T. Chen, *Nano Today*, 2011, **6**, 131–154.

- 9 B. R. Li, C. W. Chen, W. L. Yang, T. Y. Lin, C. Y. Pan and Y. T. Chen, *Biosens. Bioelectron.*, 2013, **45**, 252–259.
- 10 B. R. Li, Y. J. Hsieh, Y. X. Chen, Y. T. Chung, C. Y. Pan and Y. T. Chen, *J. Am. Chem. Soc.*, 2013, **135**, 16034–16037.
- 11 R. B. Belshe, *N. Engl. J. Med.*, 2005, **353**, 2209–2211.
- 12 H. M. So, K. Won, Y. H. Kim, B. K. Kim, B. H. Ryu, P. S. Na, H. Kim and J. O. Lee, *J. Am. Chem. Soc.*, 2005, **127**, 11906–11907.
- 13 M. J. Barry, *N. Engl. J. Med.*, 2001, **344**, 1373–1377.
- 14 W. H. King, *Anal. Chem.*, 1964, **36**, 1735–1739.
- 15 C. I. Cheng, Y. P. Chang and Y. H. Chu, *Chem. Soc. Rev.*, 2012, **41**, 1947–1971.
- 16 T. Goda, M. Tabata, M. Sanjoh, M. Uchimura, Y. Iwasaki and Y. Miyahara, *Chem. Commun.*, 2013, **49**, 8683–8685.
- 17 H. Zhao, B. Zhu, S. C. Luo, H. A. Lin, A. Nakao, Y. Yamashita and H. H. Yu, *ACS Appl. Mater. Interfaces*, 2013, **5**, 4536–4543.
- 18 L. Zhang, Z. Cao, T. Bai, L. Carr, J. R. Ella-Menye, C. Irvin, B. D. Ratner and S. Jiang, *Nat. Biotechnol.*, 2013, **31**, 553–556.
- 19 J. C. Love, L. A. Estroff, J. K. Kriebel, R. G. Nuzzo and G. M. Whitesides, *Chem. Rev.*, 2005, **105**, 1103–1169.
- 20 H. B. Akkerman, P. W. Blom, D. M. de Leeuw and B. de Boer, *Nature*, 2006, **441**, 69–72.
- 21 P. Fenter, A. Eberhardt and P. Eisenberger, *Science*, 1994, **266**, 1216–1218.
- 22 N. L. Rosi and C. A. Mirkin, *Chem. Rev.*, 2005, **105**, 1547–1562.
- 23 Z. Zhang, J. Borenstein, L. Guiney, R. Miller, S. Sukavaneshvar and C. Loose, *Lab Chip*, 2013, **13**, 1963–1968.
- 24 G. Li, G. Cheng, H. Xue, S. Chen, F. Zhang and S. Jiang, *Biomaterials*, 2008, **29**, 4592–4597.
- 25 J. Lyskawa and D. Bélanger, *Chem. Mater.*, 2006, **18**, 4755–4763.
- 26 I. Jabin, C. Mangeney, C. Roux, O. Reinaud, L. Santos, J. F. Bergamini, P. Hapiot and C. Lagrost, *Nat. Commun.*, 2012, **3**, 1130.
- 27 G. Sauerbrey, *Phys. Z.*, 1959, **155**, 206–222.
- 28 R. E. Holmlin, X. Chen, R. G. Chapman, S. Takayama and G. M. Whitesides, *Langmuir*, 2001, **17**, 2841–2850.
- 29 E. Ostuni, R. G. Chapman, M. N. Liang, G. Meluleni, G. Pier, D. E. Ingber and G. M. Whitesides, *Langmuir*, 2001, **17**, 6336–6343.
- 30 C. Dalmolin, S. C. Canobre, S. R. Biaggio, R. C. Rocha-Filho and N. Bocchi, *Electrochem. Commun.*, 2005, **578**, 9–15.
- 31 E. Venancio, C. Costa, S. Machado and A. Motheo, *Electrochem. Commun.*, 2001, **3**, 229–233.
- 32 J. Pinson and F. Podvorica, *Chem. Soc. Rev.*, 2005, **34**, 429–439.