

Low temperature electrical transport properties of RuO₂ and IrO₂ single crystals

This content has been downloaded from IOPscience. Please scroll down to see the full text.

2004 J. Phys.: Condens. Matter 16 8035

(<http://iopscience.iop.org/0953-8984/16/45/025>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 140.113.38.11

This content was downloaded on 26/04/2014 at 13:30

Please note that [terms and conditions apply](#).

Low temperature electrical transport properties of RuO₂ and IrO₂ single crystals

J J Lin^{1,2}, S M Huang¹, Y H Lin¹, T C Lee¹, H Liu³, X X Zhang³,
R S Chen⁴ and Y S Huang⁴

¹ Institute of Physics, National Chiao Tung University, Hsinchu 300, Taiwan

² Department of Electrophysics, National Chiao Tung University, Hsinchu 300, Taiwan

³ Department of Physics and Institute of Nano Science and Technology, The Hong Kong University of Science and Technology, Clear Water Bay, Kowloon, Hong Kong, People's Republic of China

⁴ Department of Electronic Engineering, National Taiwan University of Science and Technology, Taipei 106, Taiwan

E-mail: jjlin@mail.nctu.edu.tw

Received 24 June 2004, in final form 11 August 2004

Published 29 October 2004

Online at stacks.iop.org/JPhysCM/16/8035

doi:10.1088/0953-8984/16/45/025

Abstract

We have systematically measured the electrical transport properties of several RuO₂ and IrO₂ single crystals over a wide temperature range from 300 K down to 0.3 K to study the conduction mechanisms in these oxides. Our measured resistivities are in close agreement with the recent band-theory calculations for these materials. The characteristic temperatures for the acoustic-mode and optical-mode phonons are determined. Our measured magnetoresistances are positive and follow the Kohler rule, indicating that the transport properties of these oxides exhibit normal behaviour as described by the Boltzmann equation. In contrast, we do not find any signature of superconductivity down to 0.3 K, though the band-theory calculations predict a superconducting transition temperature of ~ 5 K. Magnetization measurements suggest a very low level of paramagnetic impurities in our crystals.

1. Introduction

The electronic structures and electrical transport properties of the dioxides RuO₂ and IrO₂ have recently been extensively studied. For example, the band structures of these dioxides have been calculated by several authors [1–6], while the electrical transport properties have been explicitly calculated by Glassford and Chelikowsky [5]. Experimentally, the electronic and transport properties of these metals have also been investigated over the years [7–10]. It is often accepted that the current understanding of these materials is quite complete. In particular, the electrical resistivities of these materials between 20 and 1000 K have been

measured in [9] and recently been reanalysed in [5]. On the other hand, the resistivities and magnetoresistivities of these materials have never been measured down to liquid-helium and sub-kelvin temperatures.


According to the band-structure calculations of Glassford and Chelikowsky [5], the electrical resistivity of RuO₂ at not-too-high temperatures is comprised of two terms:

- (1) the usual Bloch–Grüneisen contribution due to the coupling of electrons with acoustic-mode phonons (characterized by a coupling constant λ_{BG}); and
- (2) an additional contribution due to the coupling of electrons with optical-mode phonons (characterized by a coupling constant λ_{E}).

In this work, we report our measurements of the resistivities and magnetoresistivities of several RuO₂ and IrO₂ single crystals over a wide temperature range from 300 K down to 0.3 K. These two materials are studied together, because they crystallize in the same rutile structure and reveal similar transport properties. By comparing our experimental results with the predictions of [5], we are able to extract the values of the relevant parameters λ_{BG} , λ_{E} and the Debye temperature (θ_{D}) of these materials.

2. Experimental method

Single crystals of RuO₂ and IrO₂ were grown by the method of chemical transport reaction in a flowing oxygen system as described previously [11, 12]. The gaseous oxide, RuO₃ or IrO₃, was formed by the reaction



where M = Ru or Ir, when oxygen was passed over Ru (Ir) metal powder at a temperature of about 1200 °C (1250 °C) and at a flow rate of approximately 100 cm³ min⁻¹. The volatile MO₃ gas then decomposed and crystallized into highly ordered single crystals of MO₂ at about 1000 °C. X-ray powder diffraction analysis was performed to establish the tetragonal rutile structure, and Laue backscattering was used to identify the growth habits.

Our samples were irregular in shape. For convenience in resistance and magnetoresistance measurements, we used thin slice-shaped and needle-shaped samples. Typical slices were ~1–2 mm wide and ~0.015–0.22 mm thick. Typical needles were ~0.1–0.2 mm in diameter. Four-probe electrical contacts were made with silver paste, and the typical distance between the voltage probes was ~0.5–1.7 mm. Standard four-probe resistances and magnetoresistances were measured using a Linear Research LR-700 resistance bridge and/or a Keithley 220 current source with a Keithley 182 nanovoltmeter. The resistivities of our samples were computed and estimated to be subject to an uncertainty of about 40–50%, due to the appreciable uncertainties in the dimensions of the samples. Roughly speaking, our room temperature resistivities are ~100 μΩ cm in RuO₂ and ~50–120 μΩ cm in IrO₂. On the other hand, the resistance ratio, $R(300\text{ K})/R(4\text{ K})$, for each sample can be measured very accurately. Our values are $R(300\text{ K})/R(4\text{ K}) = 81\text{--}128$ in RuO₂ and $224\text{--}826$ in IrO₂. For this reason, table 1 lists only the values of $R(300\text{ K})/R(4\text{ K})$, but not the individual values of ρ , for each sample. It should be noted that our measured resistivities and resistance ratios are in reasonably good agreement with those previously reported by Ryden *et al* [8].

The resistance measurements of our samples were performed on a standard ⁴He dipper and an Oxford Heliox ³He cryostat. In the ⁴He dipper, the temperature was monitored using a calibrated AlGaAs thermometer. In the Heliox ³He refrigerator, a calibrated carbon glass thermometer was used for monitoring temperatures above 7 K, while a calibrated RuO₂ thermometer was used for monitoring temperatures below 7 K. The magnetoresistance

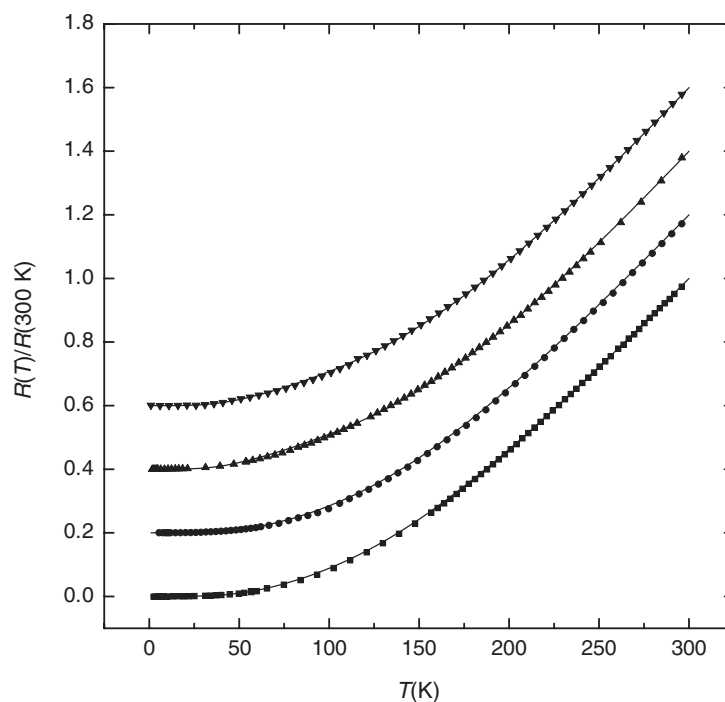


Figure 1. Normalized resistance $R(T)/R(300\text{ K})$ as a function of temperature for the (from the bottom up) RuO₂-C, RuO₂-A, IrO₂-A, and IrO₂-C single crystals. The symbols are the experimental data, and the solid curves are the theoretical fits to the sum of equations (1)–(3) as described in the text. For clarity, the data for RuO₂-A, IrO₂-A, and IrO₂-C have been shifted by +0.2, +0.4, and +0.6, respectively.

Table 1. Values of relevant parameters for RuO₂ and IrO₂ single crystals. The uncertainty in the fitted values of λ_{BG} and λ_{E} is $\pm 10\%$, while the uncertainty in the fitted values of θ_{D} (θ_{E}) is $\pm 5\%$ ($\pm 3\%$).

Sample	$R(300\text{ K})/R(4\text{ K})$	λ_{BG}	λ_{E}	θ_{D} (K)	θ_{E} (K)
RuO ₂ -A	119	0.14	0.25	401	813
RuO ₂ -B	128	0.13	0.28	404	811
RuO ₂ -C	81	0.12	0.24	401	813
IrO ₂ -A	826	0.11	0.25	280	889
IrO ₂ -B	224	0.13	0.28	289	885
IrO ₂ -C	243	0.11	0.24	296	870
IrO ₂ -D	328	0.14	0.27	292	850

measurements were performed on an Oxford SM-4000 ⁴He cryostat equipped with a 6 T split-coil superconducting magnet. The temperature was monitored with a calibrated carbon glass thermometer.

3. Results and discussion

Figure 1 shows the normalized resistances, $R(T)/R(300\text{ K})$, as a function of temperature for two RuO₂ and two IrO₂ single crystals. The symbols are the experimental data and the

solid curves are the band-theory calculations of [5]. This figure clearly demonstrates that the measured resistances are well described by the theoretical predictions. It should be noted that Ryden *et al* [8] have previously found that the resistivity in RuO₂ is essentially independent of the crystal orientation, i.e., their measured resistivities in the [100], [001], [011], and [111] directions are basically indistinguishable. Based on this observation, the orientation of our crystal with respect to the measuring current need not be specified. In practice, for all crystals, our measuring currents are essentially in the [001] direction.

In the theory of [5], the resistivity of RuO₂ is comprised of three terms. The first contribution is the usual Bloch–Grüneisen term due to the coupling of electrons with acoustic-mode phonons, and is given by

$$\rho_{\text{BG}}(T) = \frac{32\pi^2}{\hbar\Omega_p^2} k_B T \lambda_{\text{BG}} \left(\frac{T}{\theta_D}\right)^4 \int_0^{\theta_D/T} \frac{x^5 dx}{4 \sinh^2(x/2)}, \quad (1)$$

where Ω_p is the plasma frequency. The second term is an additional contribution due to the coupling of electrons with optical-mode phonons (this term is important for transition-metal oxides which contain multi-atom bases), and is given by

$$\rho_E(T) = \frac{8\pi^2}{\hbar\Omega_p^2} k_B T \lambda_E \left[\frac{\theta_E/2T}{\sinh(\theta_E/2T)} \right]^2. \quad (2)$$

That is, in this theory, the optical-mode coupling term is treated using the Einstein approximation with a single phonon frequency corresponding to the energy $k_B\theta_E$, where k_B is the Boltzmann constant. The third contribution is due to the usual electron–electron scattering which depends on the square of the temperature, and can be written as

$$\rho_{\text{ee}}(T) = A_{\text{ee}} T^2, \quad (3)$$

where A_{ee} is a temperature independent parameter. The measured normalized resistivity, $\rho(T)/\rho(300 \text{ K}) = R(T)/R(300 \text{ K})$, can then be fitted to the sum of equations (1)–(3) with λ_{BG} , θ_D , λ_E , θ_E , and A_{ee} as adjusting parameters. For real single-crystalline samples having finite residual resistances, the third term, equation (3), is *negligible* if the measuring temperature is not extremely high (e.g., several hundred kelvins and higher)⁵.

Table 1 lists the values of the fitting parameters for our samples. For comparison, Glassford and Chelikowsky obtained the values of $\lambda_{\text{BG}} \approx 0.14$, $\lambda_E \approx 0.33$, $\theta_D \approx 409 \text{ K}$, and $\theta_E \approx 787 \text{ K}$ for RuO₂. Experimentally, the ratio of our fitted values of $\lambda_{\text{BG}}/\lambda_E$, which determines the relative contribution of the acoustic-mode phonon and optical-mode phonon terms, is ≈ 0.5 for both RuO₂ and IrO₂. It should be noted that the values of θ_D for RuO₂ reported in previous measurements were 650 ± 40 and $900 \pm 50 \text{ K}$ in [7] and [8], respectively. These previous values were clearly overestimated.

As for IrO₂, the values of θ_D previously reported in [7] ($\approx 470 \text{ K}$) and [8] ($= 700 \pm 100 \text{ K}$) are significantly higher than our result of $\approx 290 \text{ K}$ (see table 1). Unfortunately, no band-structure calculations for the electronic and transport properties of IrO₂ are available in the literature.

In the presence of a magnetic field B and at liquid-helium temperatures, the magnetoresistances for all our RuO₂ and IrO₂ crystals reveal similar behaviour and are all positive. (In this work, we focus on the case where the magnetic field is applied perpendicular to the measuring current.) In low magnetic fields, the magnetoresistances vary quadratically with the field, as expected. In higher magnetic fields of the order of tens of kG, depending on temperature and the sample, the magnetoresistances increase somewhat linearly with

⁵ In practice, the resistivity due to the electron–electron scattering in transition metals is of the order of $\rho_{\text{ee}} \sim (10^{-5} \text{ K}^{-2}) T^2 \mu\Omega \text{ cm}$, where T is in kelvins, for example see [13].

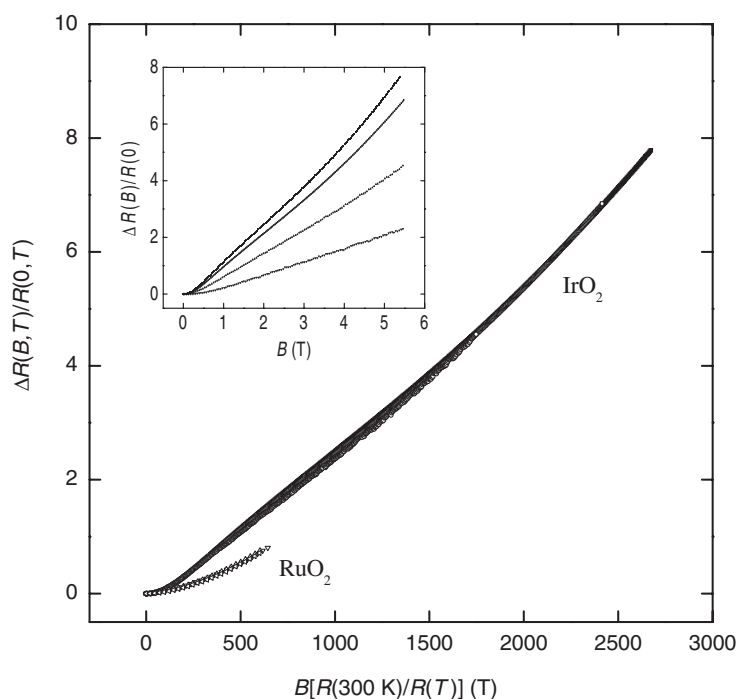


Figure 2. Normalized magnetoresistance $\Delta R(B, T)/R(0, T) = [R(B, T) - R(0, T)]/R(0, T)$ as a function of the normalized magnetic field $B[R(300\text{ K})/R(T)]$ for the RuO₂-B single crystal at 10.0, 20.0, and 30.0 K, and the IrO₂-A single crystal at 6.0, 10.0, and 20.0 K. For each crystal, the normalized magnetoresistance obeys the Kohler rule and the magnetoresistances measured at different temperatures overlap closely and (the symbols) are indistinguishable. The inset shows the normalized magnetoresistance as a function of magnetic field for the IrO₂-A single crystal at four temperatures (from the top down): 4.2, 10.0, 20.0, and 30.0 K.

increasing field up to our highest measuring field of 5.5 T. The inset of figure 2 shows the magnetoresistances as a function of magnetic field for an IrO₂ crystal at four temperatures as indicated in the caption to figure 2. Quantitatively, a plot of the normalized magnetoresistance, $[R(B, T) - R(0, T)]/R(0, T)$, versus the normalized field, $B[R(300\text{ K})/R(T)]$, indicates that the measured magnetoresistances closely obey the Kohler rule [14] below about 30 K. That is, for every sample, the normalized magnetoresistances measured at different temperatures scale with the normalized magnetic field. Above about 30 K, the contribution from the optical-mode term becomes non-negligible, and a small deviation from the Kohler rule is observed. The normalized magnetoresistances illustrating the Kohler rule for one representative IrO₂ and one RuO₂ single crystal measured at several temperatures are plotted in the main panel of figure 2. This observation of an ‘orthodox’ magnetoresistance phenomenon supports the Glassford–Chelikowsky prediction [5] that the transport properties of RuO₂ exhibit normal behaviour as described by the Boltzmann equation.

With the values of the electron–phonon coupling constants λ_{BG} and λ_{E} being determined, and assuming the renormalized Coulomb pseudopotential $\mu^* = 0.1$, one might be tempted to predict a superconducting transition temperature of ~ 5 K in RuO₂ [5, 16]. To test this conjecture, we have performed careful resistance measurements down to 0.3 K. Figure 3 shows the normalized resistance, $R(T)/R(5\text{ K})$, as a function of temperature for one IrO₂ and two RuO₂ crystals between 0.3 and 6 K. This figure clearly illustrates that the resistances

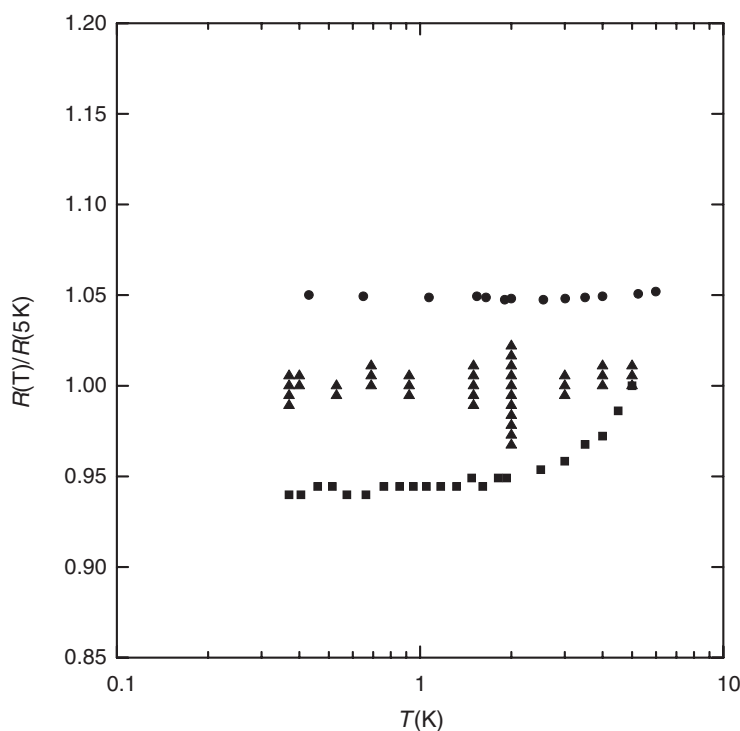


Figure 3. Normalized resistance $R(T)/R(5\text{ K})$ as a function of temperature for the $\text{RuO}_2\text{-B}$ (circles), $\text{RuO}_2\text{-A}$ (triangles), and $\text{IrO}_2\text{-B}$ (squares) single crystals below 6 K. For clarity, the data for the $\text{RuO}_2\text{-B}$ have been shifted by +0.05. The data for the $\text{RuO}_2\text{-A}$ reflect the largest possible uncertainties in our measurements due to the smallness of the sample resistance.

remain constant down to 0.3 K, with no sign of an abrupt drop to a zero resistance for any sample. The finite residual resistance reflects the existence of a low concentration of defects or impurities in the samples. Thus, to clarify whether our crystals might contain a minute amount of magnetic impurities, we have performed magnetization measurements between 2 and 300 K, using a Quantum Design SQUID magnetometer. Our measured magnetizations above several tens of kelvins are consistent with previous results [15]. Below around 35 K, however, we found a slight increase in magnetization with decreasing temperature, indicating the presence of a low level of paramagnetic impurities in the crystals. Quantitatively, our measured low temperature magnetizations are well described by the Curie law from which an estimate of a magnetic impurity level of 20 ppm in both RuO_2 and IrO_2 could be inferred, if we assume that the paramagnetic impurities are mainly due to Fe^{3+} ions. This estimate is in satisfactory consistency with the spectrographic analysis of our starting Ru and Ir metals. Generally, a level of 20 ppm of magnetic impurities would barely suppress the superconducting transition [17], if such a transition does exist initially, as speculated in [5, 16]. Whether spin fluctuations or other detrimental mechanisms (e.g., strong electron–electron interactions) might play a role in suppressing superconductivity in RuO_2 deserves further study.

4. Conclusion

We have systematically measured the resistivities of several RuO_2 and IrO_2 single crystals over a wide temperature range from 300 to 0.3 K. Our results for the resistance as a function

of temperature agree well with the recent band-structure calculations. Our magnetoresistance measurements also demonstrate that the transport properties of these dioxides exhibit normal behaviour as described by the Boltzmann equation.

Acknowledgment

This work was supported by the Taiwan National Science Council through Grant No NSC 92-2120-M-009-007.

References

- [1] Mattheiss L F 1976 *Phys. Rev. B* **13** 2433
- [2] Sasaki T A and Soga T 1981 *Physica B* **111** 304
- [3] Xu J H, Jarlborg T and Freeman A J 1989 *Phys. Rev. B* **40** 7939
- [4] Glassford K M and Chelikowsky J R 1993 *Phys. Rev. B* **47** 1732
- [5] Glassford K M and Chelikowsky J R 1994 *Phys. Rev. B* **49** 7107
- [6] Yavorsky B Yu, Krasovska O V, Krasovskii E E, Yaresko A N and Antonov V N 1996 *Physica B* **225** 243
- [7] Passenheim B C and McCollum D C 1969 *J. Chem. Phys.* **51** 320
- [8] Ryden W D, Lawson A W and Sartain C C 1970 *Phys. Rev. B* **1** 1494
- [9] Ryden W D, Reed W A and Greiner E S 1972 *Phys. Rev. B* **6** 2089
- [10] Graebner J E, Greiner E S and Ryden W D 1976 *Phys. Rev. B* **13** 2426
- [11] Huang Y S and Liao P C 1987 *Chin. J. Phys.* **25** 232
- [12] Reames F M 1976 *Mater. Res. Bull.* **11** 1091
- [13] Dugdale J S 1977 *The Electrical Properties of Metals and Alloys* (London: Edward Arnold)
- [14] Ziman J M 1960 *Electrons and Phonons* (Oxford: Clarendon)
- [15] Fletcher J M, Gardner W E, Greenfield B F, Holdaway M J and Rand M H 1968 *J. Chem. Soc. A* 653
Cotton F A and Mague J T 1966 *Inorg. Chem.* **5** 317
Guthrie A N and Bourland L T 1931 *Phys. Rev.* **37** 303
- [16] Allen P B 2000 *Handbook of Superconductivity* ed C P Poole Jr (New York: Academic)
- [17] Riblet G 1971 *Phys. Rev. B* **3** 91
Gladstone G, Jensen M A and Schrieffer J R 1969 *Superconductivity* ed R D Parks (New York: Dekker)