



ELSEVIER

Available online at [www.sciencedirect.com](http://www.sciencedirect.com)

SCIENCE @ DIRECT®

Physica C 388–389 (2003) 559–560

PHYSICA C

[www.elsevier.com/locate/physc](http://www.elsevier.com/locate/physc)

# Magnetic field dependence of the low-temperature specific heat of MgCNi<sub>3</sub>

J.-Y. Lin <sup>a,\*</sup>, H.D. Yang <sup>b</sup>, C.-Q. Jin <sup>c</sup><sup>a</sup> Institute of Physics, National Chiao Tung University, Hsinchu 300, Taiwan, ROC<sup>b</sup> Department of Physics, National Sun Yat-Sen University, Kaohsiung 804, Taiwan, ROC<sup>c</sup> Institute of Physics, Center for Condensed Matter Physics and Beijing High Pressure Research Center, Chinese Academy of Sciences, P.O. Box 603, Beijing 100080, PR China

## Abstract

The specific heat of a superconductor carries crucial signatures of its order parameter. The newly discovered superconductor MgCNi<sub>3</sub> is predicted to be unstable to ferromagnetism, and the symmetry of its order parameter symmetry is of current interest. To shed light on this issue, we have measured the low-temperature specific heat of MgCNi<sub>3</sub> in  $H$ . Careful analysis of the data suggests that  $\gamma(H) \propto H$ . Together with other physical properties, the results imply that MgCNi<sub>3</sub> is a moderate-coupling BCS superconductor.

© 2003 Elsevier Science B.V. All rights reserved.

**Keywords:** MgCNi<sub>3</sub>; Specific heat; Order parameter; The mixed state

The newly discovered superconductivity in MgCNi<sub>3</sub> has been a surprise [1]. MgCNi<sub>3</sub> can be regarded as fcc Ni with only one quarter of Ni replaced by Mg and with C sitting on the octahedral sites. With the structure so similar to that of ferromagnetic Ni, there has been theoretical speculation that MgCNi<sub>3</sub> is with strong ferromagnetic fluctuations [2]. To be compatible with the magnetic fluctuations, there is a possibility that MgCNi<sub>3</sub> has p-wave order parameter. The magnetic field dependence of  $\gamma(H)$  is sensitive to the symmetry of the order parameter [3]. For a gapped superconductor,  $\gamma(H)$  is expected to be proportional to  $H$  where  $\gamma$  is the linear coefficient of  $C$  with respect to  $T$ . For nodal superconductivity,  $\gamma(H) \propto H^{1/2}$  is predicted. It is therefore of interest to study  $C$  of MgCNi<sub>3</sub> in detail. In this paper, the magnetic field dependence of  $C$  is analyzed.

The MgCNi<sub>3</sub> sample was prepared based on the procedure described in [1]. The X-ray diffraction pattern revealed the nearly single phase of MgCNi<sub>3</sub> structure. It

is well known that  $T_c$  significantly depends on the real carbon content in the nominal MgCNi<sub>3</sub> [1]. Magnetization, specific heat, and resistivity measurements all showed a superconducting onset at about 7 K in the present sample. The resistivity transition width is less than 0.5 K, while thermodynamic  $T_c$  determined from  $C(T)$  is 6.4 K.  $C(T)$  was measured using a <sup>3</sup>He thermal relaxation calorimeter from 0.6 to 10 K with magnetic fields  $H$  up to 8 T.

The results of the specific heat measurements were reported in [4] in detail.  $\Delta C/\gamma_n T_c = 1.97$  is estimated from the anomaly at  $T_c$ . This indicates a moderate-coupling superconductivity within the BCS context. Fig. 1 shows  $C/T$  vs.  $T^2$  at low  $T$  in magnetic fields. To figure out  $\gamma(H)$ , the data was extrapolated to  $T = 0$  for  $H \geq 4$  T as indicated by the straight lines in Fig. 1. The low field data suffer contamination from the paramagnetic contribution of the impurities, and  $\gamma(H)$  can only be obtained through the attempts of the fitting. For the approximation, consider  $C(T, H) \simeq C(T, H=0) + \gamma(H)T + C_m(T, H)$ , where  $C_m$  is the paramagnetic contribution and assumed to be in the Schottky form. If we take the zero-field data between 2.5 and 4.5 K as  $C(T, H=0)$  (to

\* Corresponding author. Fax: +886-3-572-0728.

E-mail address: [ago@cc.nctu.edu.tw](mailto:ago@cc.nctu.edu.tw) (J.-Y. Lin).

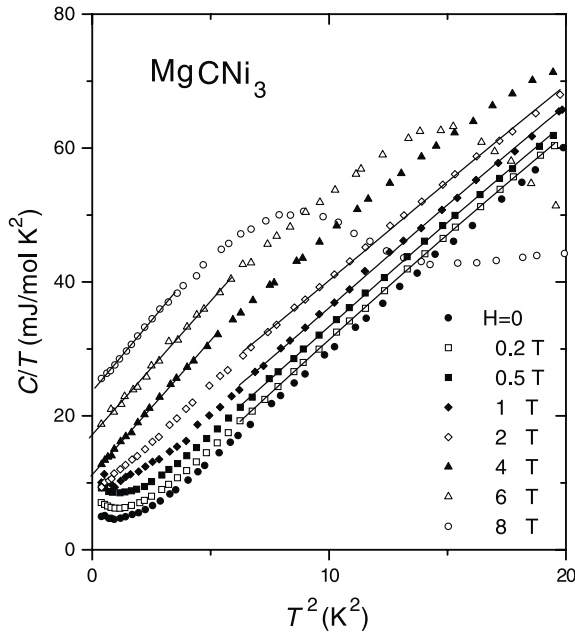


Fig. 1.  $C(T,H)/T$  vs.  $T^2$  of  $\text{MgCNi}_3$  for  $H = 0$ –8 T. The solid lines are either to extrapolate  $\gamma$  in high fields or to represent the fits mentioned in the text for low field data.

avoid the magnetic contribution at low temperatures),  $\gamma(H)$  can be estimated by fitting  $C(T,H)$  in this temperature range. The resulting  $\gamma(H)$  with  $H \leq 2$  T is shown in Fig. 2 together with the high field  $\gamma$  obtained as mentioned above.

Linearity of  $\gamma$  can be clearly seen in high  $H$  from Fig. 2, while a nonlinear  $\gamma(H)$  at low  $H$  is likely as suggested by the fits.  $\gamma(H)$  tends to revert to be linear at high  $H$  as suggested in Fig. 2. The nonlinearity in low  $H$  can be attributed to the flux line interactions [5]. The linear  $\gamma$ , together with the full superconducting gap and other evidences reported in [4], suggests a s-wave order parameter in  $\text{MgCNi}_3$ . It is noted that other form of  $C_m$  would lead to slightly different results for low field  $\gamma$  and could bring  $\gamma$  more close to the linearity. Fitting with other forms of  $C_m$  will be reported elsewhere.

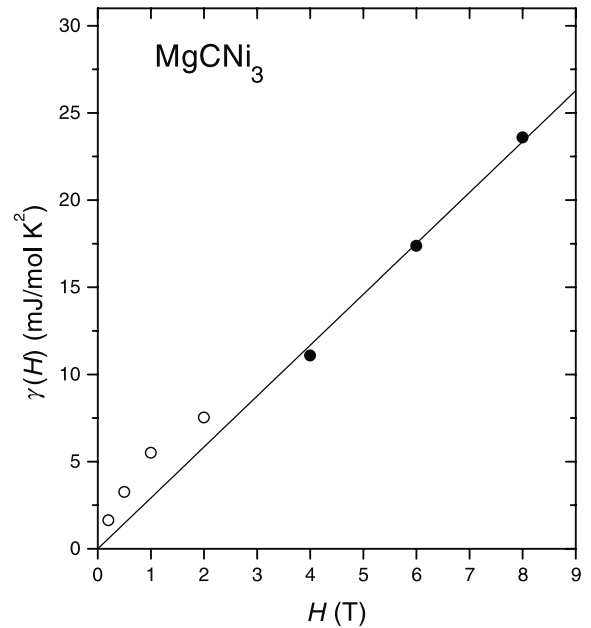


Fig. 2.  $\gamma(H)$  obtained from either extrapolation (high field) or fitting (low field).

#### Acknowledgements

This work was supported by National Science Council, Taiwan, Republic of China under contract nos. NSC90-2112-M-009-025 and NSC90-2112-M-110-012.

#### References

- [1] T. He, Q. Huang, A.P. Ramirez, K.A. Regan, N. Rogado, M.A. Hayward, M.K. Hass, J.S. Slusky, K. Inumaru, H.W. Zandbergen, N.P. Ong, R.J. Cava, *Nature* 411 (2001) 54.
- [2] H. Rosner, R. Weht, M.D. Johannes, W.E. Pickett, E. Tosatti, *Phys. Rev. Lett.* 88 (2001) 027001.
- [3] For a brief, see H.D. Yang, J.-Y. Lin, *J. Phys. Chem. Solid* 62 (2001) 1861.
- [4] J.-Y. Lin, P.L. Ho, H.L. Huang, P.H. Lin, Y.-L. Zhang, R.-C. Yu, C.-Q. Jin, H.D. Yang, *cond-mat/0202034*.
- [5] A.P. Ramirez, *Phys. Lett. A* 211 (1996) 59.